

AD-A051 721


RENSSELAER POLYTECHNIC INST TROY N Y DEPT OF MATERIA--ETC F/G 11/6
DEFORMATION AND FRACTURE OF CONTROLLED EUTECTICS CONTAINING INT--ETC(U)
FEB 78 N S STOLOFF N00014-75-C-0503

UNCLASSIFIED

| OF |
ADA
051721



END
DATE
FILMED
4 -78
DDC

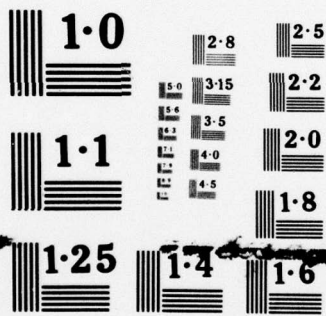

NATIONAL BUREAU OF STANDARDS
MICROCOPY RESOLUTION TEST CHART

AD A051721

AD No.
DDC FILE COPY

12

See 1473
in back

Final Report

Office of Naval Research

Contract N00014-75-C-0503, NR 031-745

DEFORMATION AND FRACTURE OF CONTROLLED
EUTECTICS CONTAINING INTERMETALLIC COMPOUNDS

Principal Investigator: N. S. Stoloff

Materials Engineering Department
Rensselaer Polytechnic Institute
Troy, New York 12181

ACCESSION for	
NTIS	White Section <input checked="" type="checkbox"/>
DDC	Buff Section <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist. AVAIL. and/or SPECIAL	
A	

DDC
RECEIVED
MAR 24 1978
D

DISTRIBUTION STATEMENT A

Approved for public release;
Distribution Unlimited

A. OVERALL OBJECTIVES OF RESEARCH

The principal aim of this research has been to define the microstructural features of aligned eutectics that can be expected to control tensile, creep and fatigue resistance. Efforts were centered upon eutectics containing intermetallic compounds because some of the principal alloys considered for high temperature structural applications (γ/γ' - δ , γ'/γ -Mo, γ' - δ , γ/γ' -TaC) contain one or more ordered intermetallic compounds, either as reinforcing composite phases or precipitate particles or both. Ordered alloys are characterized by excellent high temperature properties as a consequence of reduced diffusion rates within the compounds, which in turn reduces creep rate. In addition, the limited number of slip systems associated with long range ordered alloys leads to excellent fatigue resistance. Also, the identification of an alloy system (Ag_3Mg -AgMg), in which the degree of long range order in the Ag_3Mg phase could be altered by heat treatment, permitted a critical test of low temperature strengthening theories in eutectic composites. Finally, at the inception of this research program little attention was being paid by alloy designers to optimization of properties through control of microstructural features such as interphase spacing or distribution of a precipitated phase. Consequently, another major aim of this research has been to determine the role of interphase spacing and precipitate distribution upon mechanical properties of aligned eutectics.

B. ALLOYS CHOSEN FOR INVESTIGATION

During the early years of this program attention was centered on low-melting eutectic alloys: Ag_3Mg -AgMg, Ag-Ag₂Al and Al-Al₃Ni. Ag_3Mg -AgMg

was the most important of these, because post-solidification heat treatments could be utilized to vary the state of long range order in the Ag_3Mg phase, thereby permitting direct assessment of the role of long range order in mechanical behavior. Another important reason for choosing these low-melting alloys was the ability to vary solidification rates, and therefore interphase spacings, λ , over wide ranges so that the dependence of tensile, creep and fatigue properties on λ could be assessed.

Since 1975 we have concentrated our efforts upon several high temperature, nickel-base eutectic composites,

Nitac - Ni,10Cr,5Al-14TaC

$\gamma/\gamma'-\delta$ (0%Cr) - Ni,21Nb,2.5Al

$\gamma/\gamma'-\delta$ (6%Cr) - Ni,20Nb,6Cr,2.5Al

A Ni,Cr,Al alloy corresponding to the matrix composition of Nitac also has been tested to provide composition data. Nitac alloys have fibrous microstructures with a low volume fraction of reinforcements (about 3%). The $\gamma/\gamma'-\delta$ alloys, on the other hand, are lamellar, with 30-37% reinforcing phase. Consequently, the two alloy types offered a sharp contrast in microstructure. However, both sets of alloys were amenable to post-solidification heat treatments to alter the γ' morphology present in the as-directionally solidified alloys. The latter was utilized as a fatigue test variable, together with interphase spacing for $\gamma/\gamma'-\delta$, and test temperature, environment and frequency for Nitac. During the course of the investigation, research at Rensselaer on other fibrous aligned eutectics, notably Cotac (Co,Cr,Ni-TaC) and $\gamma'/\gamma\text{-Mo}$ (Ni,Al,Mo), provided additional data on fatigue resistance as affected by microstructure. As a result, several

review papers either on the general subject of mechanical behavior or on fatigue of eutectics were published and/or presented at technical meetings.

C. EQUIPMENT

During the course of this program several directional solidification furnaces were constructed. The first system, capable of temperatures to about 900°C by resistance heating was utilized for low-melting alloys. Later, two induction heated units were constructed.

Fatigue testing was carried out on three closed-loop Instron machines, with all tests in stress control on unnotched samples. All tests were conducted at 25°C in air (except for Al-Al₃Ni, which was tested to 410°C at several test frequencies in air), until early in 1977, when a vacuum chamber for high temperature testing was successfully completed. Since then considerable testing of Nitac was performed at 825°C in vacuum, at frequencies in the range 0.02 to 20 Hz. A limited number of constant-load creep tests also have been conducted in the range 800-950°C to identify deformation mechanisms and to determine the possible interaction between creep and fatigue processes at low cyclic frequencies.

SUMMARY OF RESEARCH ACCOMPLISHED

A. Effects of Interphase Spacing and Long Range Order on Mechanical Properties of Low-Melting Eutectics

Interphase spacing has been shown to markedly influence low temperature tensile properties, as well as fatigue resistance and high temperature creep behavior of Ag₃Mg-AgMg. Effects generally were more pronounced when Ag₃Mg was ordered, due to the influence of order in slip processes. Decreasing λ generally improves strength without impairing ductility; an exception was noted for the Al-Ag₂Al alloy in which interphase boundaries are not strong

barriers to plastic flow, so that decreasing λ actually reduced yield strength. This effect was ascribed to increasing grain size as solidification rate, R , increased. Previous to this work there had been no report in the literature of eutectic grain boundaries affecting low temperature tensile properties. In one instance (Al-Al₃Ni) a very fine interphase spacing outweighed non-alignment of the microstructure in producing high fatigue resistance. A particularly striking effect of decreasing λ on increased fatigue strength was noted in elevated temperature tests on Al-Al₃Ni. Reduced interphase spacing also improved the room temperature fatigue behavior of γ/γ' - δ , especially at high stress levels.

Creep resistance of Ag₃Mg-AgMg was improved by refining λ , but much more significant was the suppression of creep when Ag₃Mg was ordered. The stress exponent, n , in the creep equation:

$$\dot{\epsilon} = A\sigma^n e^{-Q/RT} \quad (1)$$

was not affected by order, but decreased from about 14 at high stress levels to about 3 at very low stress levels. The activation energy, Q , for creep of the alloy increased from 43 to 79 kcal/mole with order in the Ag₃Mg phase.

B. Effects of Post-Solidification Heat Treatment on Fatigue Properties

Only limited success was achieved in improving room temperature fatigue properties of Nitac and γ/γ' - δ by heat treatment to control γ' size and distribution. However, at 825°C in vacuum a significant improvement in fatigue resistance of aged Nitac was noted, relative to the as-D.S. alloy. Heat treatments also influenced crack paths in fatigue of γ/γ' - δ . The fatigue behavior

of a Ni,Cr,Al "matrix" alloy was shown to be much inferior to that of Nitac at all stress levels.

C. Elevated Temperature Creep and Fatigue Properties of Nitac

Our vacuum system has been utilized for a series of fatigue tests at 825°C, frequency = 20 Hz, on Nitac in two microstructural conditions: as-directionally solidified and solution treated and aged. The aged material exhibited superior fatigue resistance, as had previously been observed at 25°C. Additional tests run in vacuum at 825°C at frequencies of 2, 0.2 and 0.02 Hz revealed a progressive decrease in fatigue resistance with decreasing frequency. Similar results had previously been obtained for Al-Al₃Ni; for both alloys a significant creep-fatigue interaction appears to be responsible, rather than an environmental effect. Creep tests were performed at 775°C-850°C in order to determine creep parameters in the same range of temperature and peak stress as used in the fatigue experiments. Data were analyzed according to Equation 1. The activation energy, $Q = 152$ kcal/mole. The stress exponent, n , varied with temperature from 15 to 21. A high stress exponent is characteristic of eutectic alloys, as was previously described for Ag₃Mg-AgMg.

D. Fractographic Features

A notable feature of room temperature fatigue cracking in aligned eutectics is a strong tendency for slip-band cracking, also known as stage I-type cracking. This was particularly notable in Nitac (and Cotac) type alloys. Heat treatments had some effect on fracture morphology since fatigue striations were noted only in solution-treated Nitac, and then not in all tests. Striations were observed also in disordered Ag₃Mg-AgMg, but

not in this alloy in the ordered condition, for which only slip-band cracking occurred. A strong tendency for deflection of fatigue cracks parallel to the tensile axis was noted both in Al-Al₃Ni and $\gamma/\gamma'-\delta$. Interphase boundary splitting, in fact, appeared to be a major source of the extremely high fatigue resistance displayed by $\gamma/\gamma'-\delta$ (0%Cr). The addition of 6%Cr produced a partially cellular microstructure under the same growth conditions, with markedly inferior fatigue properties. However, interphase boundary splitting was noted even in the 6%Cr alloy. Fatigue resistance of $\gamma/\gamma'-\delta$ (0%Cr) was shown to be superior to that of any other eutectic alloy for which tension-tension fatigue data have been reported in the literature.

Scanning electron fractography has revealed a distinct change in fatigue mode from stage I, crystallographic cracking at room temperature for all microstructural conditions to a dimpled fracture normal to the applied stress axis at 825°C; no striations were observed at elevated temperatures. Transmission electron microscopy has been utilized to determine dislocation substructures generated by both creep and fatigue experiments. A pronounced change in dislocation substructure appearance with test frequency in fatigue could be correlated with an increased creep component at low frequencies. These results, taken together with fatigue life vs. frequency data, are strong evidence that creep-fatigue interactions play a dominant role in elevated temperature fatigue experiments.

Fractographic features for tensile and creep tests also were recorded during this program with the results published in a review paper.

TECHNICAL REPORTS

Contract N00014-67-A-0117-0010, NR 031-745

1. "Ordering and the Strength of an Aligned Ag_3Mg - AgMg Eutectic", Y. G. Kim and N. S. Stoloff, October 31, 1971.
2. "The Effects of Growth Speed and Heat Treatment on Deformation of Aligned Ag_3Mg - AgMg and $\text{Al-Ag}_2\text{Al}$ Eutectics", R. H. Bellow, Y. G. Kim and N. S. Stoloff, August 31, 1972.
3. "Creep Behavior of an Aligned Ag_3Mg - AgMg Eutectic", Y. G. Kim and N. S. Stoloff, July 1, 1973.
4. "Fatigue Behavior of an Ag_3Mg - AgMg Eutectic Composite", Y. G. Kim, G. E. Maurer and N. S. Stoloff, April 1, 1974.
- 5.* "Microstructural Effects in the Fatigue Behavior of Metals and Alloys", N. S. Stoloff and D. J. Duquette, August 31, 1974.

Contract N00014-75-C-0503, NR 031-745

1. "The Influence of Growth Rate and Temperature on High Cycle Fatigue of $\text{Al-Al}_3\text{Ni}$ ", G. E. Maurer, D. J. Duquette and N. S. Stoloff, August 1, 1975.
2. "High Cycle Fatigue of Nickel and Cobalt-Base Aligned Eutectics", N. S. Stoloff, W. A. Johnson, J. E. Grossman and C. Koburger, August 1, 1976.
3. "High Temperature Eutectic Composites: Mechanical Behavior", N. S. Stoloff, July 15, 1977.

* Number did not appear on report

PUBLICATIONS

Y. G. Kim and N. S. Stoloff, "Ordering and the Strength of an Aligned Ag_3Mg - AgMg Eutectic", Metallurgical Transactions, 3, 1391, (1972).

Y. G. Kim, R. H. Bellows and N. S. Stoloff, "The Effects of Growth Speed and Heat Treatment on Deformation of Aligned Ag_3Mg - AgMg and Al - Ag_2Al Eutectics", Proc. Conf. on In Situ Composites, Lakeville, Connecticut 2, 121, (1972).

Y. G. Kim, R. H. Bellows and N. S. Stoloff, "Fracture Mechanisms in the Lamellar Eutectic Composites", Proc. 3rd Int. Conf. on Fracture, Munich, Germany, (1973).

Y. G. Kim and N. S. Stoloff, "Long Range Order and Creep Properties of an Aligned Ag_3Mg - AgMg Eutectic", Proc. Third Int. Conf. on Strength of Metals and Alloys, Cambridge, England, 286 (1973).

Y. G. Kim, G. Maurer and N. S. Stoloff, "Fatigue Behavior of an Ag_3Mg - AgMg Eutectic Composite", Proc. Symposium on Fatigue of Composite Materials, Bal Harbour, Florida, Dec. (1973), ASTM STP 569, 210 (1975).

N. S. Stoloff and D. J. Duquette, "Microstructural Effects in the Fatigue Behavior of Metals and Alloys", CRC Reviews in Solid State Sciences, CRC Press, Cleveland, Ohio, 4, 615 (1974).

N. S. Stoloff, "Ordering Effects in Directionally Solidified Eutectic Alloys", Proc. Int. Symp. on Order-Disorder Transformations in Alloys, Tubingen, Germany, Springer-Verlag, Berlin, Germany, 476 (1974).

Y. G. Kim and N. S. Stoloff, "Creep Behavior of an Aligned Ag_3Mg - AgMg Eutectic", Met. Trans. 5, 809 (1974).

G. E. Maurer, D. J. Duquette and N. S. Stoloff, "The Influence of Growth Rate and Temperature on High Cycle Fatigue of Al - Al_3Ni ", Met. Trans. 7A, 703 (1976).

N. S. Stoloff and D. J. Duquette, "Fractographic Features in Eutectic Composites", in Fractography, ASTM STP 600, 1154 (1976).

G. E. Maurer, D. J. Duquette and N. S. Stoloff, "Fatigue Crack Initiation and Propagation in an Aligned Al - Al_3Ni Eutectic", Proc. Fourth Int. Conf. on Strength of Metals and Alloys, Nancy, France, 2, 563 (1976).

L. Klein, J. Grossman, H. Marcus and N. S. Stoloff, "Hydrogen Embrittlement of an Aligned γ/γ' - δ Eutectic Alloy", Scripta Met. 10, 889 (1976).

N. S. Stoloff, "Alloy Design for Ultrahigh Strength-Composites", in Alloy and Microstructural Design, J. K. Tien and G. S. Ansell, Editors, Academic Press, New York, 65 (1976).

R. Matera, C. Albertini and N. S. Stoloff, "The Mechanical Behavior of Aligned Eutectics at High Rates of Strain", Materials Science and Engineering 32, 267 (1978).

N. S. Stoloff, "High Temperature Eutectic Composites: Mechanical Behavior", accepted by Reviews on High Temperature Materials (1978).

J. E. Grossman and N. S. Stoloff, "Effects of Microstructure on Fatigue of γ/γ' - δ Type Eutectic Alloys", Met. Trans. 9A, 117 (1978).

N. S. Stoloff and D. J. Duquette, "Fatigue Mechanisms in Nickel and Cobalt-Base Eutectic Composites", Proc. Symp. on Fatigue Mechanisms, Kansas City, Missouri, May 22-24, 1978.

N. S. Stoloff, "Mechanical Properties of Oriented Eutectics", Proc. Ispra Course on Composite Materials (1976), Applied Science Publ. Ltd., Barking, Essex, England, to be published.

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Final Report	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER (9)
4. TITLE (and Subtitle) Final Report on "Deformation and Fracture of Controlled Eutectics Containing Intermetallic Compounds"		5. TYPE OF REPORT & PERIOD COVERED Final Technical Report 1969-Dec-1977
7. AUTHOR(s) N. S./Stoloff		6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS Materials Engineering Department Rensselaer Polytechnic Institute Troy, New York 12181		8. CONTRACT OR GRANT NUMBER(s) NO0014-75-C-0503
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Arlington, Virginia 22217		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 031-745
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE February 15, 1978
		13. NUMBER OF PAGES ten
		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release, distribution unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) (11) 15 Feb 78		
18. SUPPLEMENTARY NOTES (12) 11 p.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Fatigue, slip, fracture, creep, eutectic, dislocation, temperature, frequency, nickel, aluminum		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The results of research performed under this contract on the following aligned eutectics are summarized: Ag ₃ Mg-AgMg, Al-Ag ₂ Al, Al-Al ₃ Ni, Ni,Cr,Al-TaC (Nitac) and Ni,Nb,Cr,Al ($\gamma/\gamma'-\delta$). Tensile, fatigue and creep experiments have shown the importance of refining interphase spacing in producing increased strength. $\gamma/\gamma'-\delta$ with no Cr is shown to have the best tension-tension fatigue resistance of all aligned eutectics.		

DD FORM 1473
1 JAN 73

EDITION OF 1 NOV 68 IS OBSOLETE
S/N 0102-014-6601

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

302 125